

WUXI XINDAZHONG STEEL SHEET CO., LTD

TEST REPORT

P/I No.: FM/13/06-610
 Test Date: Sep 07, 2013
 Goods: Prime Electrolytic Tinplate
 Buyer: Y. F. S. CO.
 Seller: Famico Trading Limited

P/I Date: June 9th, 2013

Product	0.30X610(RW)X915MM
Symbol Of Classification	Prime Electrolytic Tinplate
Type Of Coating	Equal Coating
Designation Of Coating Weight	2.8/2.8g/m ²
Temper Designation	T3

Item	Standard	Result	
Tolerance Of Length (MM)	915+3	915.5	
Tolerance Of Width (MM)	610+3	611	
Tolerance Of Thickness (MM)	0.30±10%	0.305	
Temper Grade For Sngle Cold-Reduced Hardness (Hr30tm)	52~62	56	
Tin Coating (g/m ²)	Min Face: 2.45/back: 2.45	Face: 2.89	
		Back: 3.1	
Minimum Average Coating Ratio (%) To The Nominal Coating Mass (Table3)	87	87	
OIL (DOS) (g/m ²)	No Standard	2~5 mg/ m ²	
Surface Roughness (µm) (stone)	No Standard	0.35~0.6um	
Steel Type	MR		
Chemical Treatment Passivation	311		
Appearance	Plate Uniform In Thickness,Uniform And Smooth Tin Coating,Free From Flaws,Wrinkles,Rusts.	Without Defect	
Figure Of Mass	60tons	61.125tons	
Mass Of One Sheet	1.2818kg	1.2819kg	
Mass Tolerance Of One Lot	+/-5%	Pass	
Flatness	<5mm	2mm	
Out Of Squareness	<0.25 %	<0.15%	
Chemical Composition % (Steel Grade: SPCC)	C	≤0.08	
	Si	≤0.03	
	Mn	≤0.35	
	P	≤0.02	
	S	≤0.02	
	Cu	≤0.2	
Packaging	Packaging In Pallet, Wrapped With Steel.	Pass	
Marking	Symbol Of Classification And Steel Type	Electrolytic Tinplate(Spte) MR	● Pass
	Produce Date	2013-09-04	
	Inspection No.(Coil No.)	1309048713	
	Size (Thickness X Width X Length)	0.30X610X910MM	
	Tin Coating	E2.8/2.8 g/m ²	
	Temper	T3	
	Sheet Quantity / Weight	1100sheets/1410KG	
	Contract No.		
	Destination		
	Grade	A	
	Passivation	311	
	Surface Finish	R Stone Finish	
	Country Of Origin	China	
	Manufacturer Name	Wuxi Xindazhong Steel Sheet Co., Ltd	
Standard	JIS G3303-2008		

WUXI XINDAZHONG STEEL SHEET CO., LTD

TEST REPORT

P/I No.: FM/13/06-610
 Test Date: Sep 07, 2013
 Goods: Prime Electrolytic Tinplate
 Buyer: Y. F. S. CO.
 Seller: Famico Trading Limited

P/I Date: June 9th, 2013

Product	0.30X800(RW)X800MM
Symbol Of Classification	Prime Electrolytic Tinplate
Type Of Coating	Equal Coating
Designation Of Coating Weight	2.8/2.8g/m ²
Temper Designation	T3

Item	Standard	Result	
Tolerance Of Length (MM)	800+3	800.5	
Tolerance Of Width (MM)	800+3	801.5	
Tolerance Of Thickness (MM)	0.30±10%	0.295	
Temper Grade For Sigle Cold-Reduced Hardness (Hr30tm)	52-62	55	
Tin Coating (g/m ²)	Min Face: 2.45/back: 2.45	Face: 2.92	
		Back: 2.95	
Minimum Average Coating Ratio(%) To The Nominal Coating Mass(Table3)	87	87	
OIL (DOS) (g/m ²)	No Standard	2-5 mg/ m ²	
Surface Roughness (µm) (stone)	No Standard	0.35-0.6um	
Steel Type	MR		
Chemical Treatment Passivation	311		
Appearance	Plate Uniform In Thickness,Uniform And Smooth Tin Coating,Free From Flaws,Wrinkles,Rusts.	Without Defect	
Figure Of Mass	60tons	62.755tons	
Flatness	<5mm	2mm	
Mass Of One Sheet	1.5048	1.5047	
Mass Tolerance Of One Lot	+/-5%	PASS	
Out Of Squareness	<0.25 %	<0.15%	
Chemical Composition % (Steel Grade: SPCC)	C	≤0.08	
	Si	≤0.03	
	Mn	≤0.35	
	P	≤0.02	
	S	≤0.02	
	Cu	≤0.2	
Packaging	Packaging In Pallet, Wrapped With Steel.	Pass	
Marking	Symbol Of Classification And Steel Type	Electrolytic Tinplate(Spte),MR	Pass
	Produce Date	2013-09-01	
	Inspection No.(Coil No.)	1309017201	
	Size (Thickness X Width X Length)	0.30X800X800MM	
	Tin Coating	E2.8/2.8 g/m ²	
	Temper	T3	
	Sheet Quantity / Weight	1050 sheets/1580KG	
	Contract No.		
	Destination		
	Grade	A	
	Passivation	311	
	Surface Finish	R Stone Finish	
	Country Of Origin	China	
Manufacturer Name	Wuxi Xindazhong Steel Sheet Co., Ltd		
Standard	JIS G3303-2008		

WUXI XINDAZHONG STEEL SHEET CO., LTD

TEST REPORT

P/I No.: FM/13/06-610
 Test Date: Sep 07, 2013
 Goods: Prime Electrolytic Tinplate
 Buyer: Y. F. S. CO.
 Seller: Famico Trading Limited

P/I Date: June 9th, 2013

Product	0.28X710(RW)X910MM
Symbol Of Classification	Prime Electrolytic Tinplate (Spte)
Type Of Coating	Equal Coating
Designation Of Coating Weight	2.8/2.8g/m ²
Temper Designation	T3

Item	Standard	Result	
Tolerance Of LENGTH (MM)	910+3	911	
Tolerance Of WIDTH (MM)	710+3	711.5	
Tolerance Of THICKNESS (MM)	0.28±10%	0.278	
Temper Grade For Sigle Cold-Reduced Hardness (Hr30tm)	52-62	56	
Tin Coating (g/m ²)	Min Face: 2.45/back: 2.45	Face: 2.95	
		Back: 2.98	
Minimum Average Coating Ratio (%) To The Nominal Coating Mass (Table3)	87	87	
Oil (DOS) (g/m ²)	No Standard	2~5 mg/ m ²	
Surface Roughness (µm) (stone)	No Standard	0.35~0.6um	
Steel Type	MR		
Chemical Treatment Passivation	311		
Appearance	Plate Uniform In Thickness,Uniform And Smooth Tin Coating,Free From Flaws,Wrinkles,Rusts.	Without defect	
Figure Of Mass	60tons	63.4tons	
Mass Of One Sheet	1.107kg	1.108kg	
Mass Tolerance Of One Lot	+/-5%	pass	
Flatness	<5mm	2mm	
Out Of Squareness	<0.25 %	<0.15%	
Chemical Composition % (Steel Grade: SPCC)	C	≤0.08	
	Si	≤0.03	
	Mn	≤0.35	
	P	≤0.02	
	S	≤0.02	
	Cu	≤0.2	
Packaging	Packaging In Pallet, Wrapped With Steel.	Pass	
Marking	Symbol Of Classification And Steel Type	Electrolytic Tinplate(Spte), MR	Pass
	Produce Date	2013-09-02	
	Inspection No.(Coil No.)	1309028708	
	Size (Thickness X Width X Length)	0.28X710X910mm	
	Tin Coating	E2.8/2.8 g/m ²	
	Temper	T3	
	Sheet Quantity / Weight	925 Sheets/1024kg	
	Contract No.		
	Destination		
	Grade	A	
	Passivation	311	
	Surface Finish	R Stone Finish	
	Country Of Origin	China	
Manufacturer Name	Wuxi Xindazhong Steel Sheet Co., Ltd		
Standard	JIS G3303-2008		

WUXI XINDAZHONG STEEL SHEET CO., LTD

TEST REPORT

P/I No.: FM/13/06-610
 Test Date: Sep 07, 2013
 Goods: Prime Electrolytic Tinplate
 Buyer: Y. F. S. CO.
 Seller: Famico Trading Limited

P/I Date: June 9th, 2013

Product	0.28X800(RW)X800MM
Symbol Of Classification	Prime Electrolytic Tinplate (Spte)
Type Of Coating	Equal Coating
Designation Of Coating Weight	2.8/2.8g/m ²
Temper Designation	T3

Item	Standard	Result	
Tolerance Of LENGTH (MM)	800+3	801	
Tolerance Of WIDTH (MM)	800+3	801.5	
Tolerance Of THICKNESS (MM)	0.28+/-10%	0.278	
Temper Grade For Sigle Cold-Reduced Hardness (Hr30tm)	52-62	56	
Tin Coating (g/m ²)	Min Face: 2.45/back: 2.45	Face: 2.97	
		Back: 2.95	
Minimum Average Coating Ratio (%) To The Nominal Coating Mass (Table3)	87	87	
OIL (DOS) (g/m ²)	No Standard	2~5 mg/ m ²	
Surface Roughness (µm) (Stone)	No Standard	0.35~0.6um	
Steel Type	MR		
Chemical Treatment Passivation	311		
Appearance	Plate Uniform In Thickness,Uniform And Smooth Tin Coating,Free From Flaws,Wrinkles,Rusts.	Without Defect	
Figure Of Mass	60tons	60.185tons	
Mass Of One Sheet	1.405kg	1.406kg	
Mass Tolerance Of One Lot	+/-5%	pass	
Flatness	<5mm	2mm	
Out Of Squareness	<0.25 %	<0.15%	
Chemical Composition % (Steel Grade: SPCC)	C	≤0.08	
	Si	≤0.03	
	Mn	≤0.35	
	P	≤0.02	
	S	≤0.02	
	Cu	≤0.2	
Packaging	Packaging In Pallet, Wrapped With Steel.	Pass	
Marking	Symbol Of Classification And Steel Type	Electrolytic Tinplate(Spte) ,MR	Pass
	Produce Date	2013-08-30	
	Inspection No.(Coil No.)	1308308515	
	Size (Thickness X Width X Length)	0.28X800X800MM	
	Tin Coating	E2.8/2.8 g/m ²	
	Temper	T3	
	Sheet Quantity / Weight	1050 Sheets/1475kg	
	Contract No.		
	Destination		
	Grade	A	
	Passivation	311	
	Surface Finish	R Stone Finish	
	Country Of Origin	China	
Manufacturer Name	Wuxi Xindazhong Steel Sheet Co., Ltd		
Standard	JIS G3303-2008		

WUXI XINDAZHONG STEEL SHEET CO., LTD

TEST REPORT

P/I No.: FM/13/06-610
 Test Date: Sep 07, 2013
 Goods: Prime Electrolytic Tinplate
 Buyer: Y. F. S. CO.
 Seller: Famico Trading Limited

P/I Date: June 9th, 2013

Product	0.26X800(RW)X800MM
Symbol Of Classification	Prime Electrolytic Tinplate (Spte)
Type Of Coating	Equal Coating
Designation Of Coating Weight	2.8/2.8g/m ²
Temper Designation	T3

Item	Standard	Result	
Tolerance Of LENGTH (Mm)	800+3	801	
Tolerance Of WIDTH (Mm)	800+3	801	
Tolerance Of THICKNESS (Mm)	0.26±10%	0.255	
Temper Grade For Sigle Cold-Reduced Hardness (Hr30tm)	52-62	56	
Tin Coating (g/m ²)	Min Face: 2.45/back: 2.45	Face: 2.92	
		Back: 2.91	
Minimum Average Coating Ratio (%) To The Nominal Coating Mass (Table3)	87	87	
OIL (DOS) (g/m ²)	No Standard	2-5 mg/ m ²	
Surface Roughness (µm) (stone)	No Standard	0.35-0.6um	
Steel Type	MR		
Chemical Treatment Passivation	311		
Appearance	Plate Uniform In Thickness,Uniform And Smooth Tin Coating,Free From Flaws,Wrinkles,Rusts.	Without Defect	
Figure Of Mass	60tons	251.662tons	
Mass Of One Sheet	1.308kg	1.309kg	
Mass Tolerance Of One Lot	+/-5%	pass	
Flatness	<5mm	2mm	
Out Of Squareness	<0.25 %	<0.15%	
Chemical Composition % (Steel Grade: SPCC)	C	≤0.08	
	Si	≤0.03	
	Mn	≤0.35	
	P	≤0.02	
	S	≤0.02	
	Cu	≤0.2	
Packaging	Packaging In Pallet, Wrapped With Steel.	Pass	
Marking	Symbol Of Classification And Steel Type	Electrolytic Tinplate(Spte) ,MR	Pass
	Produce Date	2013-08-31	
	Inspection No.(Coil No.)	1308317226	
	Size (Thickness X Width X Length)	0.26X800X800MM	
	Tin Coating	E2.8/2.8 g/m ²	
	Temper	T3	
	Sheet Quantity / Weight	1200sheets/1570KG	
	Contract No.		
	Destination		
	Grade	A	
	Passivation	311	
	Surface Finish	R Stone Finish	
	Country Of Origin	China	
	Manufacturer Name	Wuxi Xindazhong Steel Sheet Co., Ltd	
Standard	JIS G3303-2008		

WUXI XINDAZHONG STEEL SHEET CO., LTD

TEST REPORT

P/I No.: FM/13/06-610
 Test Date: Sep 07, 2013
 Goods: Prime Electrolytic Tinplate
 Buyer: Y. F. S. CO.
 Seller: Famico Trading Limited

P/I Date: June 9th, 2013

Product	0.22X510(RW)X710MM
Symbol Of Classification	Prime Electrolytic Tinplate (Spte)
Type Of Coating	Equal Coating
Designation Of Coating Weight	2.8/2.8g/m ²
Temper Designation	T3

Item	Standard	Result	
Tolerance Of LENGTH (MM)	710+3	710.8	
Tolerance Of WIDTH (MM)	510+3	511.5	
Tolerance Of THICKNESS (MM)	0.22±10%	0.225	
Temper Grade For Siple Cold-Reduced Hardness (Hr30tm)	52-62	56	
Tin Coating (g/m ²)	Min Face: 2.45/back: 2.45	Face: 2.85	
		Back: 2.91	
Minimum Average Coating Ratio (%) To The Nominal Coating Mass (Table3)	87	87	
Oil (DOS) (g/m ²)	No Standard	2~5 mg/ m ²	
Surface Roughness (µm) (Stone)	No Standard	0.35~0.6um	
Steel Type	MR		
Chemical Treatment Passivation	311		
Appearance	Plate Uniform In Thickness,Uniform And Smooth Tin Coating,Free From Flaws,Wrinkles,Rusts.	Without Defect	
Figure Of Mass	60tons	59.6tons	
Mass Of One Sheet	0.6062kg	0.6063kg	
Mass Tolerance Of On Lot	+/-5%	pass	
Flatness	<5mm	2mm	
Out Of Squareness	<0.25 %	<0.15%	
Chemical Composition % (Steel Grade: SPCC)	C	≤0.08	
	Si	≤0.03	
	Mn	≤0.35	
	P	≤0.02	
	S	≤0.02	
	Cu	≤0.2	
Packaging	Packaging In Pallet, Wrapped With Steel.	Pass	
Marking	Symbol Of Classification And Steel Type	Electrolytic Tinplate(Spte), MR	Pass
	Produce Date	2013-08-26	
	Inspection No.(Coil No.)	1308267104	
	Size (Thickness X Width X Length)	0.22X510X710mm	
	Tin Coating	E2.8/2.8 g/m ²	
	Temper	T3	
	Sheet Quantity / Weight	1600 Sheets/970kg	
	Contract No.		
	Destination		
	Grade	MR	
	Passivation	311	
	Surface Finish	R Stone Finish	
	Country Of Origin	China	
	Manufacturer Name	Wuxi Xindazhong Steel Sheet Co., Ltd	
Standard	JIS G3303-2008		

WUXI XINDAZHONG STEEL SHEET CO., LTD

TEST REPORT

P/I No.: FM/13/06-610
 Test Date: Sep 07, 2013
 Goods: Prime Electrolytic Tinplate
 Buyer: Y. F. S. CO.
 Seller: Famico Trading Limited

P/I Date: June 9th, 2013

Product	0.21X765(RW)X765MM
Symbol Of Classification	Prime Electrolytic Tinplate (Spte)
Type Of Coating	Equal Coating
Designation Of Coating Weight	2.8/2.8g/m ²
Temper Designation	T3

Item	Standard	Result	
Tolerance Of LENGTH (MM)	765+3	766	
Tolerance Of WIDTH (MM)	765+3	766	
Tolerance Of THICKNESS (MM)	0.21±10%	0.215	
Temper Grade For Siple Cold-Reduced Hardness (Hr30tm)	52-62	56	
Tin Coating (g/m ²)	Min Face: 2.45/back: 2.45	Face: 2.58~2.64	
		Back: 2.51~2.53	
Minimum Average Coating Ratio (%) To The Nominal Coating Mass (Table3)	87	87	
Oil (DOS) (g/m ²)	No Standard	2~5 mg/ m ²	
Surface Roughness (µm) (stone)	No Standard	0.35~0.6um	
Steel Type	MR		
Chemical Treatment Passivation	311		
Appearance	Plate Uniform In Thickness,Uniform And Smooth Tin Coating,Free From Flaws,Wrinkles,Rusts.	Without Defect	
Figure Of Mass	60tons	61.21tons	
Mass Of One Sheet	0.975	0.976	
Mass Tolerance Of One Lot	+/-5%	Pass	
Flatness	<5mm	2mm	
Out Of Squareness	<0.25 %	<0.15%	
Chemical Composition % (Steel Grade: SPCC)	C	≤0.08	
	Si	≤0.03	
	Mn	≤0.35	
	P	≤0.02	
	S	≤0.02	
Packaging	Packaging In Pallet, Wrapped With Steel.	Pass	
Marking	Symbol Of Classification And Steel Type	Electrolytic Tinplate(Spte) ,MR	Pass
	Produce Date	2013-08-26	
	Inspection No. (Coil No.)	1308267201	
	Size (Thickness X Width X Length)	0.21X765X765MM	
	Tin Coating	E2.8/2.8 G/M2	
	Temper	T3	
	Sheet Quantity / Weight	1600 Sheets/1560kg	
	Contract No.		
	Destination		
	Grade	A	
	Passivation	311	
	Surface Finish	R Stone Finish	
	Country Of Origin	China	
	Manufacturer Name	Wuxi Xindazhong Steel Sheet Co., Ltd	
Standard	JIS G3303-2008		

WUXI XINDAZHONG STEEL SHEET CO., LTD

TEST REPORT

P/I No.: FM/13/06-610
 Test Date: Sep 07, 2013
 Goods: Prime Electrolytic Tinplate
 Buyer: Y. F. S. CO.
 Seller: Famico Trading Limited

P/I Date: June 9th, 2013

Product	0.20X805(RW)X840MM
Symbol Of Classification	Prime Electrolytic Tinplate (Spte)
Type Of Coating	Equal Coating
Designation Of Coating Weight	2.8/2.8g/m ²
Temper Designation	T3

Item	Standard	Result	
Tolerance Of LENGTH (Mm)	840+3	841	
Tolerance Of WIDTH (Mm)	805+3	806	
Tolerance Of THICKNESS (Mm)	0.2±10%	0.205	
Temper Grade For Sige Cold-Reduced Hardness (Hr30tm)	52-62	56	
TIN COATING (G/M ²)	Min Face: 2.45/Back: 2.45	Face: 2.85	
		Back: 2.88	
Minimum Average Coating Ratio (%) To The Nominal Coating Mass (Table3)	87	87	
Oil (DOS) (g/m ²)	No Standard	2-5 mg/ m ²	
Surface Roughness (µm) (stone)	No Standard	0.35~0.6um	
Steel Type	MR		
Chemical Treatment Passivation	311		
Appearance	Plate Uniform In Thickness,Uniform And Smooth Tin Coating,Free From Flaws,Wrinkles,Rusts.	Without Defect	
Figure Of Mass	60tons	62.465tons	
Mass Of One Sheet	1.038kg	1.039kg	
Mass Tolerance Of One Lot	+/-5%	Pass	
Flatness	<5mm	2mm	
Out Of Squareness	<0.25 %	<0.15%	
Chemical Composition % (Steel Grade: SPCC)	C	≤0.08	
	Si	≤0.03	
	Mn	≤0.35	
	P	≤0.02	
	S	≤0.02	
	Cu	≤0.2	
Packaging	Packaging In Pallet, Wrapped With Steel.	Pass	
Marking	Symbol Of Classification And Steel Type	Electrolytic Tinplate(Spte) ,MR	Pass
	Produce Date	2013-08-29	
	Inspection No.(Coil No.)	1308298515	
	Size (Thickness X Width X Length)	0.20X805X840mm	
	Tin Coating	E2.8/2.8 G/M2	
	Temper	T3	
	Sheet Quantity / Weight	1450 Sheets/1505kg	
	Contract No.		
	Destination		
	Grade	A	
	Passivation	311	
	Surface Finish	R Stone Finish	
	Country Of Origin	China	
Manufacturer Name	Wuxi Xindazhong Steel Sheet Co., Ltd		
Standard	JIS G3303-2008		

WUXI XINDAZHONG STEEL SHEET CO., LTD
TEST REPORT

P/I No.: FM/13/06-610
Test Date: Sep 07, 2013
Goods: Prime Electrolytic Tinplate
Buyer: Y. F. S. CO.
Seller: Famico Trading Limited

P/I Date: June 9th, 2013


Warehouse:



Package View:



Product View

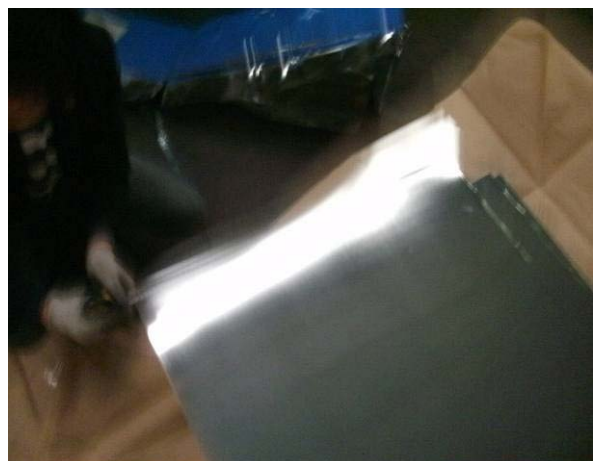

WUXI XINDAZHONG STEEL SHEET CO., LTD
TEST REPORT

P/I No.: FM/13/06-610
Test Date: Sep 07, 2013
Goods: Prime Electrolytic Tinplate
Buyer: Y. F. S. CO.
Seller: Famico Trading Limited

P/I Date: June 9th, 2013

Product Weight Check



Testing:



WUXI XINDAZHONG STEEL SHEET CO., LTD TEST REPORT

P/I No.: FM/13/06-610
Test Date: Sep 07, 2013
Goods: Prime Electrolytic Tinplate
Buyer: Y. F. S. CO.
Seller: Famico Trading Limited

P/I Date: June 9th, 2013

LOADING:

